

DEPARTMENT OF TRANSPORTATION

DIVISION OF ENGINEERING SERVICES

OFFICE ENGINEER

1727 30th Street MS-43

P.O. BOX 168041

SACRAMENTO, CA 95816-8041

FAX (916) 227-6214

www.dot.ca.gov/hq/esc/oe



*Serious Drought.
Help save water!*

February 9, 2015

07-LA,Ven-23,27,33,150-Var

07-2W8804

Project ID 0714000290

Addendum No. 1

Dear Contractor:

This addendum is being issued to the contract for CONSTRUCTION ON STATE HIGHWAY IN LOS ANGELES AND VENTURA COUNTIES AT VARIOUS LOCATIONS.

Submit bids for this work with the understanding and full consideration of this addendum. The revisions declared in this addendum are an essential part of the contract.

Bids for this work will be opened on Thursday, February 12, 2015.

This addendum is being issued to revise the *Notice to Bidders and Special Provisions*.

In the Special Provisions, Section 84-6 is added as attached.

To *Bid* book holders:

Inquiries or questions in regard to this addendum must be communicated as a bidder inquiry and must be made as noted in the *Notice to Bidders* section of the *Notice to Bidders and Special Provisions*.

Submit the *Bid* book as described in the *Electronic Bidding Guide* at the Bidders' Exchange website.

http://www.dot.ca.gov/hq/esc/oe/electronic_bidding/electronic_bidding.html

Inform subcontractors and suppliers as necessary.

Addendum No. 1
Page 2
February 9, 2015

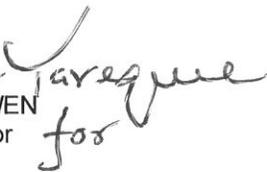
07-LA,Ven-23,27,33,150-Var
07-2W8804
Project ID 0714000290

This addendum, EBS addendum file, and attachments are available for the Contractors' download on the Web site:

http://www.dot.ca.gov/hq/esc/oe/project_ads_addenda/07/07-2W8804

If you are not a *Bid* book holder, but request a book to bid on this project, you must comply with the requirements of this letter before submitting your bid.

Sincerely,


A.K.M. Yareque
CARRIE BOWEN
District Director for

Attachment

Replace "Reserved" in the RSS for section 84-6 with:

84-6.01 GENERAL

84-6.01A Summary

Section 84-6 includes specifications for applying thermoplastic traffic stripes and pavement markings with enhanced wet-night visibility.

Thermoplastic must comply with section 84-2.

84-6.01B Submittals

Submit a certificate of compliance for the glass beads.

84-6.01C Quality Control and Assurance

Within 14 days of applying a thermoplastic traffic stripe or pavement marking with enhanced wet-night visibility, the retroreflectivity must be a minimum of 700 mcd/sq m/lx for white stripes and markings and 500 mcd/sq m/lx for yellow stripes and markings. Test the retroreflectivity using a reflectometer under ASTM E 1710.

84-6.02 MATERIALS

Thermoplastic traffic stripes and pavement markings with enhanced wet-night visibility must consist of a single uniform layer of thermoplastic and 2 layers of glass beads as follows:

1. The 1st layer of glass beads must be on the Authorized Material List under high-performance retroreflective glass beads for use in thermoplastic traffic stripes and pavement markings. The color of the glass beads must match the color of the stripe or marking to which they are being applied.
2. The 2nd layer of glass beads must comply with AASHTO M 247, Type 2.

Both types of glass beads must be surface treated for use with thermoplastic under the bead manufacturer's instructions.

84-6.03 CONSTRUCTION

Use a ribbon-extrusion or screed-type applicator to apply thermoplastic traffic stripe.

Operate the striping machine at a speed of 8 mph or slower during the application of thermoplastic traffic stripe and glass beads.

Apply thermoplastic traffic stripe at a rate of at least 0.38 lb/ft of 4-inch-wide solid stripe. The applied thermoplastic traffic stripe must be at least 0.090 inch thick.

Apply thermoplastic pavement marking at a rate of at least 1.06 lb/sq ft. The applied thermoplastic pavement marking must be at least 0.100 inch thick.

Apply thermoplastic traffic stripe and both types of glass beads in a single pass. First apply the thermoplastic, followed immediately by consecutive applications of high-performance glass beads and then AASHTO M 247, Type 2, glass beads. Use a separate applicator gun for each type of glass bead.

You may apply glass beads by hand on pavement markings.

Distribute glass beads uniformly on traffic stripes and pavement markings. Apply high-performance glass beads at a rate of at least 6 lb/100 sq ft of stripe or marking. Apply AASHTO M 247, Type 2, glass beads at a rate of at least 8 lb/100 sq ft of stripe or marking. The combined weight of the 2 types of glass beads must be greater than 14 lb/100 sq ft of stripe or marking.

84-6.04 PAYMENT

Not Used